

# Evaluation of the Performance of Local Cements with Imported Class 'G' Cement for Oil Well Cementing Operations in Ghana\*

E. Broni-Bediako, O. F. Joel and G. Ofori-Sarpong

---

Broni-Bediako, E., Joel, O. F. and Ofori-Sarpong, G. (2015), "Evaluation of the Performance of Local Cements with Imported Class 'G' Cement for Oil Well Cementing Operations in Ghana", *Ghana Mining Journal*, Vol. 15, No. 1, pp. 78 - 84.

---

## Abstract

Portland cement is the most commonly used cement in the oil and gas industry and it accounts for about 99% of all primary cementing operations throughout the world. For Portland cement to qualify as oil well cement, the chemical and physical properties must meet the required standards of the American Petroleum Institute (API). This research evaluates the performance of three locally manufactured cement samples and imported class G cement sample for oil and gas well cementing operations in Ghana. The paper details results of API specification tests and the physical properties of the local cements with the imported class G cement. The results indicated that locally manufactured cements have the potential to be used for cementing oil and gas wells. However, further tests should be conducted to ascertain their stability under High Pressure, High Temperature (HPHT) conditions.

**Keywords:** Compressive strength, Free fluid, Portland cement, Rheology, Thickening time

## 1 Introduction

Portland cement is a hydraulic product made by burning and grinding a mixture of calcareous and argillaceous materials, such as limestone and clay, limestone and shale, limestone and marl, chalk and clay or limestone and iron blast furnace slag (Morgan, 1987). Portland cement is made up of the four major clinker minerals, namely: tricalcium silicate ( $C_3S$ ); dicalcium silicate ( $C_2S$ ); tricalcium aluminate ( $C_3A$ ); and tetracalcium aluminoferrite ( $C_4AF$ ) to which 3-5% gypsum ( $CaSO_4 \cdot 2H_2O$ ) is added (Sasaki *et al.*, 1986; Lea, 1970; Lu *et al.*, 1993; Saasen *et al.*, 1994, Hibbeler *et al.*, 2000). Chemically,  $CaO$ ,  $SiO_2$ ,  $Al_2O_3$  and  $Fe_2O_3$  constitute about 80% of Portland cement. The other significant minor oxides are  $MgO$ ,  $SO_3$ ,  $K_2O$ , and  $Na_2O$  (Lea, 1970; Atiemo, 2012). Although Portland cement is primarily a construction material (Morgan, 1987) it is the most commonly used cement in the oil industry (Bett, 2010). It accounts for about 99% of all primary cementing operations (Joel, 2013) throughout the world (DiLullo *et al.*, 1994; Thiercelin *et al.*, 1997; Magarini *et al.*, 1999). In oil well cementing, Portland cement is used primarily as an impermeable seal material. It is used as a seal to secure and structurally support casing string inside the well (Heinold *et al.*, 2002; Zhang *et al.*, 2010) and prevent fluid communication between the various underground fluid-containing layers or the production of unwanted fluids into the well which can lead to casing corrosion (Heinold *et al.*, 2002; Sauki and Irawan, 2010).

For Portland cement to qualify as oil well cement, the chemical and physical properties must meet the

standards set by the American Petroleum Institute (API). In Ghana, imported class G cement is used for the oil and gas wells cementing operations. Cementing of oil/gas well is a capital-intensive project, and the cost of getting the imported cement is quite enormous. Therefore efforts have been made to study the potential of three locally manufactured cements for oil and gas well cementing operations. The purpose of this research is to evaluate the possibility of utilising locally manufactured cement for oil/gas well cementing operations in Ghana. This investigation is an effort to compare the physical properties of locally manufactured cement in Ghana with the class G cement.

## 2 Materials and Methods

### 2.1 Materials

Three brands of cement available on the Ghanaian market and commonly used by Ghanaians for construction purposes were purchased from retail outlets in Aflao in the Volta Region, Buipe in Northern Region and Tarkwa in the Western Region. The imported sample (class G cement) was obtained from Schlumberger Oil Services Company in Ghana. Distilled water was used for the cement slurry formation.

### 2.2 Experimental Design

Laboratory experiments were performed on local cement slurry to determine the potential of locally manufactured cement. The cement slurry and specimen preparation were carried out by closely following API Specification 10A. The physical

---

\*Manuscript received March 23, 2015  
Revised version accepted May 12, 2015

properties were determined by closely following API Specification 10A and API Recommended Practice 10B (Anon, 1997; 2013). The physical properties tests conducted included thickening time, compressive strength, free fluid, and rheology of the cement slurry. Three brands of locally manufactured cement (CEM A, CEM B and CEM C) and imported class G cement (CEM G) were investigated at the testing conditions specified in API Specification 10A (Table 1).

**Table 1 Experimental Conditions and Slurry Composition (API Specification)**

<i>Test Conditions</i>	
Bottom Hole Static Temperature (BHST), °F (°C)	140 (60)
Bottom Hole Circulating Temperature (BHCT), °F (°C)	125 (52)
Bottom Hole Pressure, psi (MPa)	5160 (35.6)
Heat Up Time, min	28
<i>Slurry Composition</i>	
Water Type	Distilled
Water Requirement, gal/sk (m <sup>3</sup> /t)	4.98 (0.442)
Cement Weight, %bwoc	100
Slurry Weight, ppg (kg/m <sup>3</sup> )	15.9 (1905)
Mixing Fluid, gal/sk (m <sup>3</sup> /t)	4.98 (0.442)
Yield, cu.ft/sk (m <sup>3</sup> /t)	1.14 (0.76)

### 2.3 Thickening Time Testing

The results of the laboratory thickening time tests provide an indication of the length of time that cement slurry would remain pumpable (Alp and Akin, 2013). That is, the time after initial mixing when the cement can no longer be pumped (Salam *et al.*, 2013). Consistency of cement slurry is expressed in Bearden units of consistency (Bc) (Alp and Akin, 2013). The Thickening Time (TT) test was performed in a High-Pressure High-Temperature (HPHT) Consistometer that is usually rated at pressure up to 30 000 psi (206.8 MPa) and temperatures up to 400 °F (204 °C). The cement slurry was mixed according to API procedures and then placed in a slurry cup into the consistometer for testing. The testing pressure and temperature were controlled to simulate the conditions the slurry will encounter in the well. The test concluded when the slurry reached a consistency considered un-pumpable in the well. The maximum consistency during 15 minutes to 30 minutes after the initiation of the test and the time for the cement slurry to reach consistency of 100 Bc were recorded (Anon, 1997; 2013) as shown in Fig. 1.

### 2.4 Free Fluid Testing

The intention of a free fluid test is to help determine the quantity of free fluid that will gather on the top of cement slurry between the time it is placed and the time it gels and sets up (Joel, 2009).

The cement slurries were preconditioned in a Model 165AT Atmospheric Consistometer for thirty minutes. The preconditioned slurry was remixed within 10 seconds and poured into a 500 ml graduated flask according to API Specification 10A (Anon, 2013). The mouth of the flask was sealed and then placed on a vibration free surface for 2 hours. The slurry was examined for any free fluid on the top of the cement column. This free fluid was decanted and measured with a syringe to determine the percent of free water ( $\phi$ ) based on the weight and the specific gravity of the cement using Equation (1).

$$\phi = (V_{FF}) \times S_g \times \frac{100}{m_s} \quad (1)$$

where  $V_{FF}$  is the volume of free fluid collected (supernatant fluid), expressed in millilitres;  $S_g$  is the specific gravity, and  $m_s$  is the initially recorded mass of the slurry in grams.

### 2.5 Moisture Content Testing

The moisture content of the cement sample were determined in accordance with API Specification for Drilling Fluid Materials (Anon, 2004). About 10 g of the cement was placed in a covered container (petri-dish) of known weight ( $m_1$ ) and weighed ( $m_2$ ). The container containing the cement was uncovered and together with the cover was placed in an electric oven and dried at 221 °F (105 °C) for 30 minutes. The container with the cement was taken out, covered and placed in a desiccator for about 15 minutes to cool, after which it was reweighed ( $m_3$ ). The Moisture Content (MC) of the sample was calculated as in Equation (2).

$$MC = \frac{m_2 - m_3}{m_3 - m_1} \times 100 \quad (2)$$

### 2.6 Compressive Strength Testing

Compressive strength is one of the properties used to test the reliability of cementing and is the ability of a material to withstand deformation when load is applied (Falode *et al.*, 2013). Higher compressive strength generally means lower porosity and increased durability (Alp and Akin, 2013). Insufficient compressive strength means casing failures are more likely and the life span of the well can be dramatically reduced (Huwel *et al.*, 2014). There are two common methods for determining the compressive strength of a cement slurry; non-destructive and destructive. Destructive method was employed in this research. The destructive test indicates how the cement sheath will withstand the differential pressures in the well. The main advantage with this type of method is that an exact value of compressive strength can be determined

(Huwel *et al.*, 2014).

The prepared samples were poured into a four square inch moulds and puddled for 27 times per specimen with a puddling rod and then cured at 140 °F (60 °C) using Thermo Scientific Precision 180 Series Water Bath. The samples were cured for 8 hours before they were cooled and then crushed with Carver Model 3851 Manual Press. The resultant pressures were read from the pressure gauge and the compressive strengths were calculated using Equation (3).

$$\text{Compressive Strength (psi)} = \frac{\text{Force (pounds)}}{\text{Area (square inch)}} \quad (3)$$

## 2.7 Rheology Testing

Rheology of cement slurries is of great importance for the design, construction and quality of primary cementing. Knowledge of the rheological properties is necessary to assess the possibilities for mixing and pumping cement slurries, and to predict the effect of wellbore temperature on slurry placement (Boškovic *et al.*, 2013). According to Shahriar (2011), the fundamental knowledge of oil well cement slurry rheology is necessary to evaluate the ability to remove mud and optimise slurry placement. Incomplete mud removal can result in poor cement bonding, zone communication and ineffective stimulation treatment (Bannister, 1980). The Rheology of fluids also has a major effect on solids setting and free fluid properties and also on the friction pressures (Joel, 2009). Because rheological testing is typically conducted at atmospheric pressure, the maximum temperature is limited to about 190 °F (88 °C) (Anon, 1997). The shear stress and shear rate behaviour of slurry at different temperatures was measured in this test. The rheological properties of the fluid samples used in this study were measured using Fan Viscometer Model 35A. The properties of interest studied included Plastic Viscosity ( $\mu_p$ ) and Yield Point ( $\tau_o$ ). The plastic viscosity and the yield point value were obtained using Equations (4) and (5) respectively (Darley and Gray, 1983; Anon, 1997).

$$\mu_p \text{ (cp)} = 1.5(\theta_{300} - \theta_{100}) \quad (4)$$

$$\tau_o \text{ (lb/100ft}^2\text{)} = \theta_{300} - \mu_p \quad (5)$$


Where  $\theta_{300}$  is 300 rpm dial reading and  $\theta_{100}$  is 100 rpm dial reading.

## 3 Results and Discussion

### 3.1 Thickening Time Analysis

Thickening time is an essential parameter for designing a successful cement job. If the cement slurry remains liquid over an extended period of time and functions as a solid when it stops flowing, in a reasonable time, it will be suitable for more jobs (Roshan and Asef, 2010). Fig. 1 shows the results of the thickening time of the four cement samples using the well conditions stated in API Specification 10A (Table 1).

From Fig. 1, it could be seen that at a consistency of 100 Bc, the setting period for CEM B is shorter, followed by CEM A, CEM C and finally the imported class G. Generally, the entire locally manufactured cements appeared to have shorter setting time or pump shorter as compared to the imported class G cement. This implies that more additives would be required to bring up the thickening time results of locally manufactured cements to the level of the imported class G cement. For example, for high temperature wells, more concentrations of retarders would be needed to bring up the thickening time results.

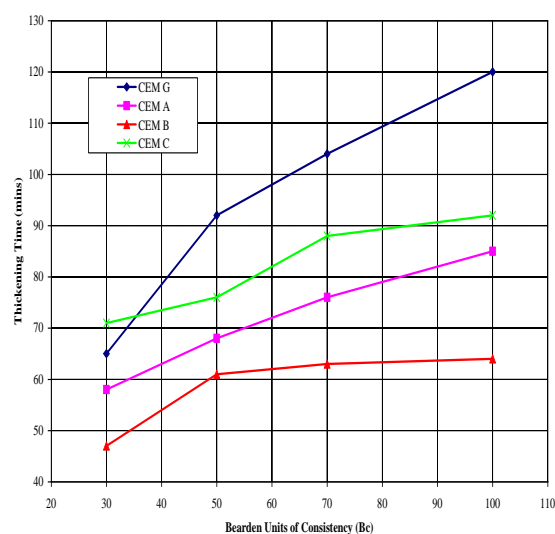

**Fig. 1 Thickening Time vs. Consistency**

Among the three local cements tested, CEM C appeared to pump longer than CEM A and CEM B. CEM C met the API requirement set for oil well cement, at a consistency of 100 Bc (Fig. 1). This implies that less retarder is required for CEM C than CEM A and CEM B if it is to meet the thickening time of the imported class G cement. According to Shahrudin *et al.* (1993), the higher the tricalcium aluminate content, the higher the rate of reaction during the hydration period of a cement. Therefore the difference in setting time could be due to the difference in tricalcium aluminate content of the cement. Chemically, locally manufactured cements will have the highest

amount of tricalcium aluminate and, therefore, would have a high rate of reaction during their hydration period, causing the cement slurries to set at shorter times than imported class G (CEM G) cement containing lower tricalcium aluminate.

The characteristics of these local cements are not different from other local cements as confirmed in other earlier works done by Mfonnom *et al.* (2009) and Joel (2009a) on local cement in Nigeria. According to the API Specifications 10A (Anon, 2013), the maximum consistency during 15 minutes to 30 minutes period after the initiation of test should be 30 Bc. The imported class G cement had the highest consistency value during the 15 minutes to 30 minutes period after the initiation of the thickening time test compared to the local cements, but generally all the cement samples tested satisfied the API requirement (Table 2).

**Table 2 Consistency during Fifteen to Thirty Minutes Period**

Cement Type	CEM G	CEM A	CEM B	CEM C	API
Consistency (Bc)	23	9	19	14	Max 30

### 3.2 Free Fluid Analysis

Free fluid (water) is one of the most important factors that should be as low as possible in cementing operations especially after the cement sets. Test results indicated in Table 3 show that there is no big difference in the free fluid results for all the cements tested in terms of the API recommended standard as both the locally manufactured samples and imported sample were below API standard. However, imported class G had the highest free fluid content as compared to the locally manufactured cements (Table 3). The higher value of free fluid content of class G cement could be due to poor handling which could have resulted to exposure to a lot of moisture. These results were confirmed by the moisture content of each sample. The moisture content of imported sample (CEM G) was higher followed by the local cements; CEM A, CEM B, and CEM C in the same order as the free fluid (Table 4).

**Table 3 Free Fluid at BHCT of 125 °F (52 °C)**


Cement Type	CEM G	CEM A	CEM B	CEM C	A PI
Free Fluid (%)	3.96	1.05	0.65	0.2	5.9

**Table 4 Moisture Content of Cement Samples**

Readings (g)	CEM G	CEM A	CEM B	CEM C
Weight of Container ( $m_1$ )	30.85	30.85	30.85	30.85
Weight of Cement and Container ( $m_2$ )	40.85	40.85	40.85	40.85
Weight of Dry Cement and Container ( $m_3$ )	40.72	40.78	40.79	40.82
<b>Moisture Content (%)</b>	<b>1.32</b>	<b>0.70</b>	<b>0.60</b>	<b>0.30</b>

### 3.3 Compressive Strength

Compressive strength of the set cements is important as it commonly represents the overall quality of cements. Higher compressive strength generally means lower porosity and increased durability (Nelson, 1990). Fig. 2 shows the results of the compressive strength test cured at 140 °F (60 °C) for 8 hours for all the cement samples.

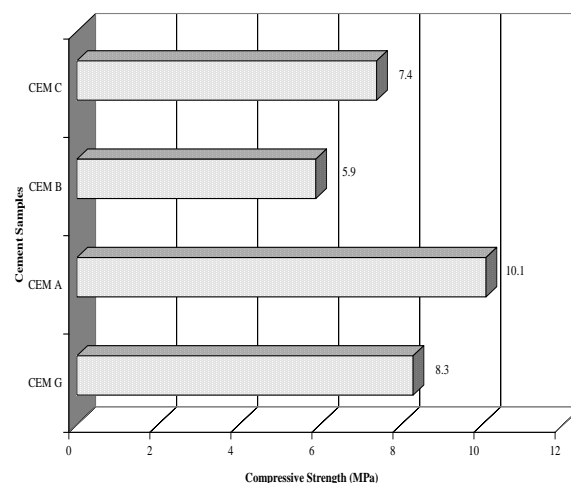

**Fig. 2 Compressive Strength of Cement Cured at 140 °F (60 °C) for 8 Hours**

Early stage compressive strength was more pronounced in locally manufactured CEM A than the imported class G cement and the rest of the locally manufactured cements. CEM A had a better compressive strength than the imported class G. This could be attributed to tricalcium aluminate ( $C_3A$ ). Because  $C_3A$  has a faster rate of reaction during hydration and a faster setting time (Fig. 1), its early stage compressive strength is expected to be higher. Surprisingly, locally manufactured cements CEM B and CEM C proved otherwise, as their compressive strengths were lower than imported class G though they have shorter setting period. Generally, none of the cement samples met API minimum requirement which is a minimum of 1500 psi (10.3 MPa) at 140 °F (60 °C) for 8 hours.

### 3.4 Rheological Properties

Table 4.5 presents the results of rheology test conducted at BHCT of 125 °F (52 °C). The basic reason for determination of rheological properties was to predict plastic viscosity and yield point values. The rheological values obtained from the local cement samples compared favourably with that of the imported cement. No gelation was observed at Bottom Hole Circulating Temperature (BHCT) of 125 °F (52 °C) for all the cement samples. In almost all the tests conducted, the values of the Plastic Viscosity (PV) were below 100 cp (100 mPa.s), which according to Abbas *et al.* (2014) is desirable to keep cement slurry pumpable. The values of the Yield Point (YP) calculated also showed that all the slurries were pumpable at 125 °F (52 °C).

**Table 5 Rheological Properties of Local and Imported Cement Samples**

Rheology @ BHCT of 125 °F(52 °C)	CEM G	CEM A	CEM B	CEM C
300 rpm	74	121	174	95
200 rpm	67	107	155	82
100 rpm	58	87	135	65
6 rpm	20	28	28	20
3 rpm	15	18	25	18
Plastic Viscosity, cp (mPa.s)	24 (24)	51 (51)	58.5 (58.5)	45 (45)
Yield Point, lb/100 ft <sup>2</sup> (Pa)	50 (24)	70 (34)	115.5 (55.3)	50 (24)

### 4 Conclusions and Recommendations

From the research it could be concluded that:

- (i) Locally manufactured cement CEM A proved to have faster early compressive strength development and lower free fluid content than imported class G cement. However, CEM A pumps shorter than imported class G.
- (ii) Locally manufactured cement CEM B proved to have suitable free fluid properties for oil well cementing than imported class G Cement. Both cements met API specification for free fluid. In terms of compressive strength and thickening time, class G cement proved to be better than CEM B, though both cements could not meet API specifications.
- (iii) Locally manufactured cement CEM C proved to have better free fluid properties than imported class G. In terms of compressive strength and thickening time, class G cement proved to be better than CEM C. However, CEM C met API

minimum value for thickening time, but pumped shorter when compared to class G.

- (iv) Rheological values obtained from the locally manufactured cements compared favourably with that of the imported cement. No abnormal gelation was experienced for both the local cements and the imported class G cement.

For the investigated properties, and at the stated conditions of temperature and pressure, CEM A compares favourably with class G in respect of API specifications, followed by CEM C and CEM B in terms of their potential for oil and gas well cementing.

It is recommended that further tests be conducted on locally manufactured cements on the chemical properties and also confirm stability for High Pressure and High Temperature (HPHT) operations.

### Acknowledgements

The authors are very grateful to the Management of Halliburton and POCEMA LTD, Nigeria and Mr. Anthony John of Halliburton and POCEMA Lab Staff for their immense contribution during the laboratory analysis in Port Harcourt, Nigeria.

### References

- Abbas, G., Irawan, S., Kumar, S., Memon, R. K. and Khalwar, S. A. (2014), "Characteristics of Oil Well Cement Slurry using Hydroxypropylmethylcellulose", *Journal of Applied Sciences*, Vol. 14 (11), pp. 1154 – 1160.
- Alp, B. and Akin, S. (2013), "Utilization of Supplementary Cementitious Materials in Geothermal Well Cementing" *Proceedings of Thirty-Eighth Workshop on Geothermal Reservoir Engineering*, Stanford University, Stanford, California, pp. 1 - 7
- Anon (1997), *American Petroleum Institute (API) Recommended Practice 10B for Testing Well Cements*, American Petroleum Institute, Washington D. C., USA, 134 pp.
- Anon (2004), *Specification for Drilling Fluid Material*", *American Petroleum Institute (API) Specification 13A*, Sixteenth Edition, API Publishing Service, Washington D.C., 66 pp.
- Anon (2013), *American National Standard Institute/American Petroleum Institute (ANSI/API) Specification 10A for Cements and Materials for Well Cementing*, API Publication Services, Washington D. C., 38 pp.
- Atiemo, E. (2012), "Studies on the Effect of Selected Local Admixtures on Essential Properties of Cement for Housing

- Construction”, *PhD Thesis*, Kwame Nkrumah University of Science and Technology, Kumasi, Ghana, 174 pp.
- Bannister, C. E. (1980), “Rheological Evaluation of Cement Slurries: Methods and Models”, *Society of Petroleum Engineers Annual Technical Conference and Exhibition*, SPE 9284, Dallas, Texas, pp. 1 - 16.
- Bett, E. K. (2010), “Geothermal Well Cementing, Materials and Placement techniques”, *Geothermal Training Programme- Report 10*, pp. 99 - 130.
- Boškovic, Z., Cebašek V. and Gojkovic, N. (2013), “Application of Local Cement for Cementing Oil Wells in the South Eastern Region of the Pannonian Basin”, *Archives for Technical Sciences*, Vol. 8(1), pp. 35 - 39.
- Darley, H.C. H. and Gray, G. R. (1983), *Composition and Properties of Drilling and Completion Fluid*, Gulf Professional Publishing, 5<sup>th</sup> Edition, U.S.A, 653 pp.
- DiLullo, G. and Gino, A. (1994), “A Sound Alternative for Oil Well Cementing”, *Offshore South East Asia 10th Conference and Exhibition World Trade Centre*, Technical Paper No. 94021, Singapore, pp.1 - 7.
- Falode, O. A., Salam, K. K., Arinkoola, A. O. and B. M. Ajagbe (2013), “Prediction of Compressive Strength of Oil Field Class G Cement Slurry using Factorial Design”, *Journal of Petroleum Exploration Production Technology*, Vol. 3, pp. 297 - 302.
- Heinold, T., Dilenbeck, R. and Rogers, J. (2002), “The Effect of Key Cement Additives on the Mechanical Properties of Normal Density Oil and Gas Well Cement Systems”, *Society of Petroleum Engineers Asia Pacific Oil and Gas Conference and Exhibition*, SPE 77867, Melbourne, Australia, pp. 1 - 12.
- Hibbeler, J., Rae, P., Gilmore, T. and Weber, L. (2000), “Using Alternative Sources of Oilwell Cement”, *International Association of Drilling Contractors/Society of Petroleum Engineers (IADC/SPE) Asia Pacific Drilling Technology Conference*, SPE 62746, Kuala Lumpur, Malaysia, pp. 1 - 10.
- Huwel, J. P. E., Faustino, V. and Roberts, R. (2014), “Cement Compressive Strength Development Drastically Affected by Testing Procedure”, *Proceedings of American Association of Drilling Engineers Fluid Conference and Exhibition*, Houston, Texas, pp. 1 - 5.
- Joel, O. F. (2009), “The Secondary Effects of Lignosulfonate Cement Retarder on Cement Slurry Properties”, *Journal of Engineering and Applied Sciences*, Vol. 4, No. 9, pp. 1 - 7.
- Joel, O. F. (2009a), “Comparative Study of Local Cement with Imported Class “G” Cement for Cementing of Oil Well in Nigeria – A Case Study”, *International Journal of Engineering*, Vol. 3(4), pp. 1 - 10.
- Joel, O. F. (2013), “Tapping the Untapped Wealth in our Backyard: Pathway to Local Content Development”, *Inaugural Lecture Series No. 104*, University of Portharcourt, Nigeria, pp. 29 - 30.
- Lea, F. M. (1970), *The Chemistry of Cement and Concrete*, Edward Arnold, London, pp. 414 - 453.
- Lu, P., Sun, G. and Young, J. F. (1993), “Phase Composition of Hydrated DSP Cement Pastes”, *Journal of the American Ceramic Society*, Vol. 76(4), pp. 1003 – 1007.
- Magarini, P., Lanzetta, C. and Galletta, A. (2009), “Drilling Design Manual”, *Eni - Agip Division*, pp. 97 - 107.
- Mfonnom, G. A., Puyete, T. Y. and Joel, F. O. (2009), “Utilization of Local Cement as an Alternative Source of Oil and Gas Well Cement - A Case Study on Dangote and Elephant Cements”, *Technical Papers of Offshore West Africa (OWA) Conference*, Nigeria, pp. 1 - 22.
- Morgan, B. E. (1958), “API Specification for Oilwell Cements”, *Drilling and Production Practice Conference*, API-58-0831, New York, pp. 1 - 8.
- Nelson, E. B., Baret, J. F. and Michaux, M. (1990), “Cement Additives and Mechanism of Action”, In *Well Cementing*, E. B. Nelson (Ed.), Elsevier Science Publishers, Amsterdam, pp. 3 - 37.
- Roshan, H. and Asef, M. R. (2010), “Characteristics of Oil Well Cement Slurry Using CMC”, *Journal of Society of Petroleum Engineers Drilling and Completion*, SPE 11446, Vol. 25 (3), pp. 328 - 335.
- Saasen, A., Haugom, J. O. and Johansen, E. (1994), “The Effect of Gypsum and Anhydrite on Rheological Properties of Cement Slurries”, *Annual Transaction of the Nordic Rheology Society*, Vol. 2, pp. 85 - 87.
- Salam, K. K., Arinkoola, A. O., Ajagbe, B. and Sanni, O. (2013), “Evaluation of Thickening Time of Oil Field Class G Cement Slurry at High Temperature and Pressure using Experimental Design”, *International Journal of Engineering Sciences*, Vol. 2(8), pp. 361 - 367.
- Sasaki, S., Kobayashi, W. and Okabayashi, S. (1986), “Strength Development of 2CaO/SiO<sub>2</sub>-Silica Cement under High-Temperature and High-Pressure Conditions”, *Journal of Society of Petroleum Engineers Production Engineering*, SPE 13406, Vol. 1 (1), pp. 42 - 48.
- Sauki B. A. and Irawan, S. (2010), “Effects of Pressure and Temperature on Well Cement Degradation by Supercritical CO<sub>2</sub>”, *International Journal of Engineering and Technology*, Vol. 10, No. 4, pp. 47 - 55.
- Shahriar, A. (2011), “Investigation on Rheology of Oil Well Cement Slurries”, *Unpublished PhD*

*Thesis*, The University of Western Ontario, Ontario, Canada, 251 pp.

Shahrudin, S., Samsuri, A., Suhiami, A., Nasir, A. S, and Ahmad, Z. (1993), "Possibility Studies of Using Local Cement in Oil and Gas Well Cementing Operations in Malaysia", [http://eprints.utm.my/4029/1/SKMB\\_T\\_60007062016310.pdf](http://eprints.utm.my/4029/1/SKMB_T_60007062016310.pdf). Accessed: January 8, 2014, pp. 1- 9.

Thiercelin, M. J., Darguad, B and Baret, J. F (1997), Cement Design Based on Cement Mechanical Response", *Society of Petroleum Annual Conference and Exhibition*, 38598, San Antonio, Texas, 1p.

Zhang, J., Weissinger, E. A., Peethamparan, S. and Scherer, G. W. (2010), "Early Hydration and Setting of Oil Well Cement", *Cement and Concrete Research*, Vol. 40, pp. 1023 - 1033.

## Authors



**Eric Broni-Bediako** is currently a Lecturer at the Petroleum Engineering Department of University of Mines and Technology, Tarkwa, Ghana. He holds MSc Degree in Petroleum Engineering from African University of Science and Technology, MPhil and BSc in Mining Engineering from University of Mines and Technology. Eric Broni-Bediako is a PhD candidate at the University of Mines and Technology, Tarkwa, Ghana. His research focuses on the possibility of using local cement for cementing operations in Ghana.



**Dr Ogbonna F. Joel** is a Professor and a Director at Centre for Petroleum Research and Training, Institute of Petroleum Studies, University of Port Harcourt, Nigeria. He holds a PhD from River State University of Science and Technology, Nigeria and MSc from University of Benin, Nigeria. He has more than eighteen years industry, teaching and research experience in drilling operations with specialisation in design and field applications of drilling, cementing and stimulation fluids. He is a subject expert in sustainability principles to the management of environmental issues and pollution control in the oil and gas industry; possess strong research and laboratory management capabilities. He is a member of Nigerian Society of Chemical Engineers (NSChE) and Nigerian Society of Engineers (NSE).



**Dr Grace Ofori-Sarpong** is a Senior Lecturer of Mineral Engineering and currently, Head of Department for Petroleum Engineering at University of Mines and Technology, Ghana. She holds a Bachelor of Science Degree in Metallurgical Engineering and a Master of Science Degree in Environmental Resources Management, both from the Kwame Nkrumah University of Science and Technology, Kumasi, Ghana. She also has a PhD in Energy and Mineral Engineering from the Pennsylvania State University, USA. Her areas of research interests include microbial-mineral interaction, recovery of precious metals, microwave processing, water quality monitoring and mine waste management. She is member of the Women in Science and Engineering (WISE), USA, Society for Mining, Metallurgical and Exploration, USA, and Society of Petroleum Engineers (SPE).