



## Recovery of Chromium (III) from Tannery wastewater

\*M. ALI AWAN, M. A. BAIG, \*JAVED IQBAL, M. R. ASLAM; NAVEED IJAZ

*Institute of Environmental Science and Engineering (IESE), National University of Sciences & Technology (NUST), Rawalpindi, Pakistan*  
Fax No: 92-51-9271597 E-mail: ali.awan@mail.com

*\* Pakistan Environmental Protection Agency (PEPA), Islamabad, Pakistan*

**ABSTRACT:** Three aqueous oxidants, Hydrogen peroxide, Sodium Hypochlorite and Calcium Hypochlorite were employed independently in oxidizing Chromium (III) containing tannery wastewaters to soluble chromate ( $\text{CrO}_4^{2-}$ ) under alkaline conditions. The amount of chromate recovered was determined via spectrophotometry. Hydrogen peroxide was potentially a suitable oxidant as it could recover chromate ( $\text{CrO}_4^{2-}$ ) up to 98% (from synthetic  $\text{Cr}^{3+}$  solution) and 88% (from effluent I). The percentage recoveries by the hypochlorites were lower than those by hydrogen peroxide i.e. for NaOCl the recoveries were up to 94% (from synthetic  $\text{Cr}^{3+}$  solution) and 67% (from effluent I), similarly for  $\text{Ca}(\text{OCl})_2$  90% (from synthetic  $\text{Cr}^{3+}$  solution) and 49% (from effluent I). For all three oxidants complete (100%) recovery could not be achieved despite different experimental conditions (temperatures and oxidation time). The results clearly indicate that hydrogen peroxide is the most efficient among the three oxidants@JASEM

Leather tanning is one of the main sectors in Pakistan's leather industry (consisting of tannery, shoemaking, furs, and leather products). About 90% of its products are exported in finished form (CCP, Pakistan's Leather Industry). There are some 600 tanneries in the formal sector and an equally large number of tanneries in the informal sector. Leather tanneries in Pakistan produce all three categories of waste: wastewater, solid waste and air emissions. However, wastewater is by far the most important environmental challenge being faced by Pakistan's tanneries (Iqbal, 1998). Although the exact quantity varies widely between tanneries, a normal requirement of around 50-60 liters of water per kilogram of hide is suggested (Iqbal 1998). Tannery wastewater is highly polluted in terms of biochemical oxygen demand (BOD), chemical oxygen demand (COD), suspended solids, settleable solids, total kjeldhal nitrogen, conductivity, sulphate, sulphide and chromium (Iqbal, 1998). The values of these parameters are very high as compared to the values mentioned in the National Environmental Quality Standards (NEQS) set by the Government of Pakistan (CCP, 1999). In about 80% of the cases untreated tannery effluent is discharged directly into recipient water bodies or onto open land and only 115 is discharged into municipal sewers that also drain into natural water bodies without any treatment. Traditionally 60 - 70% chrome applied in the form of BCS (Basic Chromium Sulphate) are absorbed by the hides and skins during process and the remaining is discharged as waste. Under certain environmental conditions, Cr III may be oxidized to Cr VI compounds (Pettine, 1990) and (Fendrof, 1992), carcinogenic compounds. Such compounds become threat to the environment (Chuan, 1996). The

recovery of chromium could help in overcoming environmental deterioration. Oxidation of the chromium containing wastewater under basic conditions is considered to be suitable for the recovery of chromium as chromate. In this work three different oxidizing agents i.e. Hydrogen peroxide ( $\text{H}_2\text{O}_2$ ), Sodium Hypochlorite (NaOCl) and Calcium Hypochlorite  $\{\text{Ca}(\text{OCl})_2\}$  would be used to recover chromium in the form of  $\text{CrO}_4^{2-}$  solution. The optimum dosage of selected reagents used would determine cost of the process.

### MATERIAL AND METHODS

The actual tanning effluents (1 and 2) were collected in plastic containers (from tanning drums and discharge pipes) from tanneries on Sambrial road, Sialkot. The samples were analyzed for COD, BOD, total solids, and metals (Mn, Cd, Cr, Zn, Ni, Cu, Pb, Co, Fe, Na and K) using standard methods (Eaton, 1995) including Atomic Absorption spectrophotometer, Varian. Two effluents containing relatively higher chromium concentration were selected for the recovery purpose. Since, we were interested in recovering chromium (Cr III) as chromate ( $\text{CrO}_4^{2-}$ ) and determining its concentration spectrophotometrically, we first determined its maximum wavelength ( $\lambda_{\text{max}}$ ) on SPECTROSONIC<sup>R</sup> GENEYSIS<sup>TM</sup> 5 spectrophotometer<sup>e</sup> and the value obtained was 372nm. The original Merck hydrogen peroxide, sodium and calcium hypochlorites solution were used for the recovery. Exact concentrations of the three oxidants were determined by standardizing them against a 0.1M sodium thiosulphate solution. A standard solution (synthetic) of  $\text{CrCl}_3$  of the concentration 100-mg/L was prepared. Then with the help of balanced equations (stoichiometric) the

\* Corresponding author

**Table 1.** Parameters obtained from the analysis of actual tanning effluents ( results are in mean of replicate measurements)

Parameter	NEQS	E - 1	E - 2
pH	6-9	3.1	4.5
Conductivity mS	-	43.7	7.5
COD, mg/L	150	3413	609
Sulphate, SO <sub>4</sub> <sup>2-</sup> mg/L	600	4221.6	1846
Phosphate, PO <sub>4</sub> <sup>3-</sup> mg/L	-	707	982
TDS, mg/L	3500	91972	6456
TSS, mg/L	150	294	70
Manganese, mg/L	1.5	0.821	0.411
Cadmium, mg/L	0.1	0.262	0.296
Chromium, mg/L	1.0	2877	220
Zinc, mg/L	5.0	1.021	0.105
Nickel, mg/L	1.0	1.445	0.797
Copper, mg/L	1.0	0.49	0.397
Lead, mg/L	0.5	1.49	0.665
Cobalt, mg/L	-	0.173	0.062
Iron, mg/L	2.0	0.786	1.404
Sodium, mg/L	-	127.6	106.9
Potassium, mg/L	-	21.73	12.11

NEQS = regulatory levels; E - 1 and 2 are effluents


amount of H<sub>2</sub>O<sub>2</sub> and NaOH required were calculated. A 100mL of synthetic Cr III solution was taken in a 250mL Erlenmeyer flask and the calculated amount (38.5mg) of NaOH was added to bring its pH>9. Cr III produced thick green precipitates of Cr(OH)<sub>3</sub>. 0.99mL H<sub>2</sub>O<sub>2</sub> (original conc. 10000mg/L) solution was then added and the flask contents were heated for 5 minutes at 100°C. The solution was then left for 5 minutes to complete reaction. The concentration of chromate (produced) was found from a calibration curve prepared by standard solutions of sodium chromate on SPECTROSONIC<sup>R</sup> GENEYSIS<sup>TM</sup> 5 spectrophotometer. The total chromium concentrations of the two tanning samples were 2877mg/L and 220mg/L respectively. These were diluted to 100mg/L. 100mL of both the samples were taken 250mL Erlenmeyer flasks and oxidized with H<sub>2</sub>O<sub>2</sub> as described for synthetic solution. The same steps were repeated at two more temperatures, 25 and 50°C with longer oxidation duration i.e. 90 and 1440 minutes. The above procedural steps are applied first on the synthetic Cr III and then on the two tanning samples while treating them independently with (i). NaOH plus sodium hypochlorite and (ii). CaO plus calcium hypochlorite.

## RESULTS AND DISCUSSION

Table-1 represents the overall picture obtained from the analysis of the two actual tanning effluents along with the NEQS (regulatory levels). The most alarming values are for TDS, COD and chromium and are a real threat to the environment. These effluents also contained sodium sulphide, sodium chloride, lime, formic acid, sulphuric acid, sodium formate etc. like a

typical tannery wastewater (Mayer, 1997). Addition of a base (NaOH or CaO) to the Cr III solutions (both synthetic and actual effluents) produced thick green precipitates of Cr(OH)<sub>3</sub>. The pH of the samples was raised automatically to around 9.5 during this addition. It is essential that the oxidizing agents added should react completely with Cr(OH)<sub>3</sub> precipitates. In order to determine the time required for complete oxidation, the process was carried out at three different temperatures.

The oxidation capabilities of the three oxidants at different temperatures and oxidation durations are given in Table-2. It was observed that the maximum recovery was achieved at higher temperature or even at lower temperature for longer period. In summer, the temperature in Sialkot (study area) is around 40°C. If the reaction time is increased to 30 hours the best results could be achieved. The effect of pH on the recovery was also studied in this work. As already mentioned, pH of the samples automatically rises when an alkali is added. The pH was then adjusted to 6.5 by adding 1:1 HCl solution but at this pH precipitates [Cr(OH)<sub>3</sub>] got dissolved; hence the recovery was not possible. pH was also adjusted around 8 but at this occasion less denser precipitates of Cr(OH)<sub>3</sub> were formed and hence the recovery was lower. The maximum recovery was only achieved when pH of the samples was around 9.5. It was observed that the maximum recovery was obtained utilizing hydrogen peroxide as oxidizing agent. It caused least interference in the oxidation process because it does not contain either metallic cation or chlorine (as hypochlorites did). The recovered CrO<sub>4</sub><sup>2-</sup> was in the form of yellow solution and its concentration was determined spectrophotometrically. In any sample 100 per cent recovery could not be obtained because the treatment of Cr III with NaOH or CaO formed very minute hydrolytic polymers Cr-O-Cr and Cr-OH-Cr along with bulk Cr(OH)<sub>3</sub> (James, 2000). These hydrolytic polymers are not oxidizable and were present in the form of green precipitates.

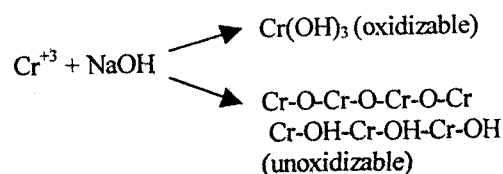

Other reasons for not achieving 100% recovery could be that a) The presence of some other metals (in low concentrations) in the effluents along with chromium. Added H<sub>2</sub>O<sub>2</sub> might had also been consumed in their oxidation. b) The Sulfides present in excess would also oxidize to Sulfates. c) Formation of certain insoluble precipitates such as CaCrO<sub>4</sub>, NiCrO<sub>4</sub>, Fe<sub>2</sub>(CrO<sub>4</sub>)<sub>3</sub>, PbCrO<sub>4</sub>, CuCrO<sub>4</sub>, ZnCrO<sub>4</sub> etc. and d)

The presence of other interfering substances such as formic acid.

**Table-2:** Oxidation at different temperatures and oxidation durations

Oxidant	Sample (Initial Conc. 100mg/L)	Temperature (Treatment)	Duration (min)	% Age Recovery	
Hydrogen peroxide	Syn - Cr (III)	100°C	5	98	
		50°C	90	96	
		25°C	1410	95	
	E - 1	100°C	5	88	
		50°C	90	62	
		25°C	1410	58	
	E - 2	100°C	5	84	
		50°C	90	63	
		25°C	1410	80	
	Sodium Hypochlorite	Syn - Cr (III)	100°C	5	94
			50°C	90	91
			25°C	1410	90
E - 1		100°C	5	67	
		50°C	90	41	
		25°C	1410	39	
E - 2		100°C	5	65	
		50°C	90	44	
		25°C	1410	41	
Calcium Hypochlorite		Syn - Cr (III)	100°C	5	90
			50°C	90	87
			25°C	1410	85
	E - 1	100°C	5	49	
		50°C	90	23	
		25°C	1410	17	
	E - 1	100°C	5	49	
		50°C	90	27	
		25°C	1410	21	

*Syn = synthetic; E - 1 and 2 are effluents*

For all the samples treated with sodium hypochlorite, the percentage recovery was lower than that with hydrogen peroxide. For calcium hypochlorite the recovery was even lower than that by sodium hypochlorite. The main reasons for this were the same as discussed above.

In the case of calcium hypochlorite a small portion of recovered chromate was converted into insoluble  $\text{CaCrO}_4$ . Unrecovered chromium existed as insoluble salts. Such insoluble precipitates were also observed (James, 2000). These insoluble precipitates can be easily separated and if at all, they are released would settle down in drain and would not be problematic as they are insoluble precipitates.

### SUMMARY

The recovery using hydrogen peroxide ( $\text{H}_2\text{O}_2$ ) is economical, environment friendly and simple. The cost expended on the recovery of chromate from a 1L

100mg/L Cr III synthetic solution showed that the value for  $\text{H}_2\text{O}_2$  is 19 times lower than that for  $\text{NaOCl}$  and 8 times lower than that for  $\text{Ca(OCl)}_2$ . In tanneries the concentration of chromium (tanning drum) after chrome tanning may range from 3000-6000 mg/L depending on the size of the drum. The drum normally used in small and medium size tanneries are of 8 feet diameter and 8 feet in length. Therefore, we can estimate the amount of water in a drum and in turn the amount oxidant plus alkali required for the recovery. The advantages associated with the use of  $\text{H}_2\text{O}_2$  are:

(a). The percentage recovery is higher than other two oxidants.

(b). Only hydrolytic polymers exist as non-recoverable matter, the remaining is converted to chromate whereas in case of  $\text{Ca(OCl)}_2$  insoluble  $\text{CaCrO}_4$  is formed resulting in the loss of chromate.

(c). The  $\text{H}_2\text{O}_2$  present in excess has no adverse effect on recovery and it eliminates itself with the passage of time whereas hypochlorites leave toxic  $\text{OCl}^-$ ,  $\text{Cl}_2$ ,  $\text{HCl}$  and halogenated hydrocarbons in the effluents.

(d).  $\text{H}_2\text{O}_2$  is cheaper and easily available in the market.

(e). Reaction time is less than the other two oxidants.

The recovered chromate can be reused in the in the tanning process in various proportions. Besides the recovered chromate can be converted to other useful products such as lead and barium chromates, dichromate, chromic oxide, chromium sulphate, etc.

*Acknowledgement:* Assistance of Mr. Muhammad Basharat and Idrees Ahmad of IESE in metal analysis is acknowledged.

### REFERENCES

Chuan, M C; Liu, J C (1996). Release behavior of chromium from tannery sludge. *Water Research* 30, 932-938

Cleaner Production Program (CCP), Pakistan's Leather Industry, <http://www.cpp.org.pk/etpibrchr/brochure-leather.pdf>

Cleaner Production Program (CCP) (1999) Revised National Environmental Quality Standards (NEQS). <http://www.cpp.org.pk/legal/RevisedNEQS.pdf>

Eaton, A D; Clesceri, L S; Greenberg, A E (1995). *Standard Methods for the Examination of Water and Wastewater*, 19<sup>th</sup> Edition. American Public Health Association. USA.

Fendrof, S E; Zasoski, R J (1992). Chromium III oxidation by  $\text{MnO}_2$ , Characterization. *Environmental Science & Technology*, 26, 79-85.

Iqbal, M.(1998). TheLeather ector, Environmental Report,  
<http://www.cpp.org.pk/etpirpt/LeatherSectorReport.pdf>

James, MG; Beattie, J K; Kennedy, B J (2000).  
Recovery of chromate from electroplating sludge.  
Waste Manage Res: 18, 380-385.

Mayer, E. (1997). A System for Recovery and Reuse  
of Chromium from Spent Tanning Liquor using  
Magnesium Oxide and Sulphuric Acid.  
[www.unido.org/stdoc.cfm?did=50374](http://www.unido.org/stdoc.cfm?did=50374)

Pettine, M; Millero, F J (1990). Chromium speciation  
in seawater: The probable role of hydrogen peroxide.  
Limnology and Oceanography 35, 730-736